

We have successfully developed a broadband transverse electrooptic modulator (fig. L.4.2). The element was fabricated using the in-house grown LiNbO_3 crystal for this purpose. The dimensions of the crystal element are: $17 \times 2 \times 0.8 \text{ mm}^3$. The half wave voltage of the modulator was 89 volts, measured at 632 nm wavelength (set up shown in fig. L.4.1). The modulator module was tested for analog modulating signals up to 2 MHz frequency range at 632 nm (representative fig. L.4.3). The characteristics of the module are: Type: Broadband EO modulator, Bandwidth: $\sim 450 \text{ MHz}$, Insertion loss: $\sim 0.9 \text{ dB}$ and efficiency $\sim 10\%$. Some improvements are required in the electroding, electrical contacts, terminal and packaging of the device in order to demonstrate it at higher frequencies.

(Contributed by: S. Kar, R. Bhatt, K.S. Bartwal; bartwal@cat.ernet.in and T.P.S.Nathan)

L.5 Sol-gel based anti-reflection coatings on Nd: glass laser rods & wedge-shaped optics using spin coater

Sol-gel coatings, due to their high damage threshold and ease of coating of large area substrates with high spatial uniformity at room temperature, are finding increasing applications in fabrication of optics for high power lasers. In high-power pulsed Nd: glass laser systems used for laser plasma interaction studies, a large number of cylindrically shaped laser rods and disks with anti-reflection (AR) coated end surfaces are used to set up master oscillator and power amplifiers. The entrance and exit faces of the laser rods in such systems are usually cut at an angle of a few degrees (typically 3 to 5°) with respect to the plane normal to the rod axis to avoid depletion of stored energy because of parasitic oscillations. AR coatings are mostly deposited by vacuum dielectric coating technique using either electron beam evaporation or ion beam sputtering. In these coating methodologies, the substrate is required to be heated to a temperature of about 200 °C to produce a good adhesion of the coating to the substrate to achieve high abrasion resistance, and it has to be simultaneously rotated around its axis to obtain a high spatial uniformity of the coating on the surface. However, for large size laser rods, these simultaneous operations in a vacuum chamber become quite difficult. We have developed and characterized sol-gel AR coatings on wedge-shaped optics [R. Pareek, A.S. Joshi, P.D. Gupta, P.K. Biswas and S. Das, *Optics and Laser Technology* 37, 369 (2005)] and used them to make good quality sol-gel AR coatings on wedged Nd: glass laser rods.

A double layer coating design involving two different materials was used to deposit AR coating. Zirconia and silica sols were chosen for depositing the high and the low refractive

index material layers, respectively. Coatings were deposited on flat circular substrates of BK-7 glass and the Nd: phosphate glass laser rods using a spin coater (CONVAC GmbH model 1001). Refractive index of the sol films was measured to be 1.645 and 1.450 for zirconia (2 wt%) and silica (6 wt%) sols, respectively. Calibration curves of physical thickness deposited on BK-7 flat glass substrates versus rotation speed of the spin-coater were obtained for the two sols for the rotation speed in the range of 1000 to 4000 rpm. These were used to select appropriate rotation speeds to deposit the desired thickness of the two sols on flat as well as wedge substrates.

Specular reflection spectra at the centre of the AR coated BK-7 glass substrates of the different wedge angles are shown in the fig L.5.1. It is seen that the reflectivity spectrum from the wedge substrates shifts towards the higher wavelength side for increasing values of the wedge angle. This data was used to decide appropriate rotation speeds for a particular wedge angle to achieve reflectivity minimum at the lasing wavelength of 1054 nm. A 50 mm diameter, 300 mm long Nd: glass laser rod with end surfaces cut at 3° was AR coated with a reflectivity of $\sim 0.7\%$ at 1054 nm.

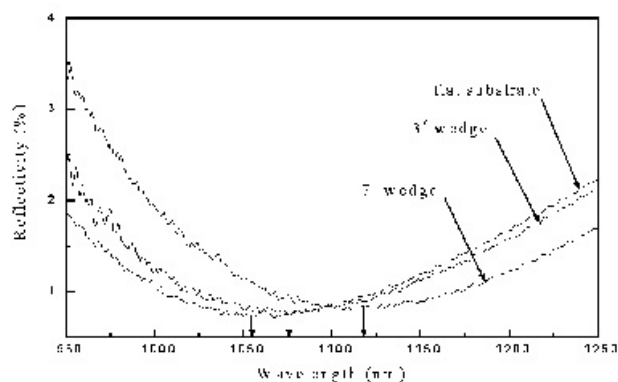


Fig. L.5.1 Specular reflection spectra obtained at the centre of the AR coated substrates of different wedges angles

(Contributed by: R. Pareek and A. S. Joshi; asjoshi@cat.ernet.in)

L.6 Highly stable operation of regenerative amplifier for Table Top Terawatt Nd:glass laser system

Ultra-short laser pulses of energy several orders of magnitudes higher than that available directly from a mode locked oscillator, are required for many investigations and applications. Such pulses are amplified using the Chirped Pulse Amplification technique. In such a system, one stretches a short pulse in time by frequency chirping, amplifies the same